

INCONEL® alloy MA 758 is an oxide-dispersion-strengthened (ODS) nickel-chromium superalloy, made by mechanical alloying. It is a development of the well-established aerospace superalloy, INCONEL alloy MA 754, with its chromium content increased to 30%, to improve its performance in corrosive environments at high temperatures. The alloy's high-temperature strength is enhanced by the use of yttrium oxide for dispersion strengthening.

In addition to its strength and corrosion resistance at high service temperatures, it is readily fabricated and can be hot formed into a range of shaped components for use in thermal processing applications.

INCONEL alloy MA 758 is used in some of the most demanding applications for high-temperature metals and alloys. For example, for furnace skid rails to transport heavy steel billets and slabs, at 1260°C (2300°F) and above, and for the bowl-shaped components used to spin molten glass, at around 1200°C (2200°F), to produce fiberglass for thermal insulation.

It is used in a range of thermal processing applications, from furnace components, such as hearth rollers, to jigs, tools, and other fabrications for supporting workpieces through heat-treatment processes.

It has been specified for a fuel atomizer application in diesel engines.

Publication No. SMC-075

Copyright © Special Metals Corporation 2004 (Sept 04)

INCONEL® and INCOLOY® are trademarks of the Special Metals Corporation group of companies.

The data contained in this publication is for informational purposes only and may be revised at any time without prior notice. The data is believed to be accurate and reliable, but Special Metals makes no representation or warranty of any kind (express or implied) and assumes no liability with respect to the accuracy or completeness of the information contained herein. Although the data is believed to be representative of the product, the actual characteristics or performance of the product may vary from what is shown in this publication. Nothing contained in this publication should be construed as guaranteeing the product for a particular use or application.

Table 1 - Nominal Composition (wt.%)

Chromium.....	30.0
Carbon.....	0.05
Aluminum.....	0.3
Titanium.....	0.5
Yttrium oxide (Y ₂ O ₃).....	0.6
Iron.....	1.0
Nickel.....	Balance*

*Reference to the 'balance' of an alloy's composition does not guarantee this is exclusively of the element mentioned, but that it predominates and others are present only in minimal quantities.

Made by Mechanical Alloying

Mechanical alloying, the process used to produce INCONEL alloy MA 758, is a dry, high-energy ball milling operation that produces composite metal powders with controlled, extremely fine, microstructures.

Typically, a mixture of commercially available metal powders, master alloy powders, and a very fine refractory oxide powder (Y₂O₃ for INCONEL alloy MA 758) is charged into the mill.

During the process, metal powder particles are trapped between the rapidly colliding grinding balls and, under the controlled conditions of mechanical alloying, are cold-welded together. The oxide powder particles are trapped within the composite powders along the weld interfaces between the different composite constituents. The cold-welding leads to the build-up of larger powder particles. This is followed by a fracturing stage in which the larger composite powder particles are broken down. A balance is achieved between the welding and the fracturing so that the overall particle size of the composite powder remains nearly constant. The interplay between the welding and fracturing subdivides and kneads the ingredients to create a uniform distribution of the oxide and other metallic components.

Mechanically alloyed powders are consolidated by placing them in sealed cans for extrusion or hot pressing, followed by conventional hot- and cold-working processes. A final anneal at very high temperatures is required to develop the stable, coarse, grain structure suitable for the most demanding stress-rupture applications.

INCONEL® alloy MA 758



Physical & Thermal Properties

Table 2 - General Properties

Density, g/cm ³	8.14
lb/in. ³	0.294
Melting Point (Solidus), °F	2507
°C	1375

Table 3 - High-Temperature Electrical Resistivity

Temperature		Electrical Resistivity	
°F	°C	ohm-circ. mil/ft	microhm-cm
71	22	685.1	113.9
200	93	692.0	115.0
400	204	699.5	116.3
600	316	707.7	117.6
800	427	714.6	118.8
1000	538	723.5	120.3
1200	649	725.5	120.6
1400	760	721.4	119.9
1600	871	722.1	120.0
1800	982	724.2	120.4
2000	1093	731.7	121.6
2200	1204	740.6	123.1

Hot rolled plate, 2400°F (1315°C)/1h/AC, transverse orientation.

Table 4 - High-Temperature Thermal Expansion Properties

Temperature		Linear Expansion	Coefficient of Expansion	
°F	°C	in/in x 10 ⁻³	in/in/°F x 10 ⁻⁶	cm/cm/°C x 10 ⁻⁶
77	25	0	—	—
200	92	0.85	6.93	12.47
300	149	1.57	7.06	12.71
400	204	2.31	7.16	12.89
500	260	3.10	7.32	13.18
600	316	3.89	7.44	13.39
700	371	4.72	7.57	13.63
800	427	5.58	7.72	13.90
900	482	6.45	7.84	14.11
1000	538	7.30	7.91	14.24
1100	593	8.22	8.04	14.47
1200	649	9.25	8.23	14.81
1300	704	10.10	8.26	14.87
1400	760	11.05	8.35	15.03

Reference temperature, 77°F (25°C)

Expansion testing in accordance with ASTM E228-85.

Hot-rolled plate, 2400°F (1315°C)/1h/AC, transverse orientation.

Mechanical Properties

The mechanically alloyed ODS superalloys are well known for their exceptionally high strength at high service temperatures. Figure 1 shows the creep strength of INCONEL alloy MA 758 along with two other mechanically alloyed products, INCONEL alloy MA 754 and INCOLOY alloy MA 956, and a typical cast iron-chromium-nickel heat-resisting alloy. At high temperatures, the three superalloys are all significantly stronger than the cast alloy.

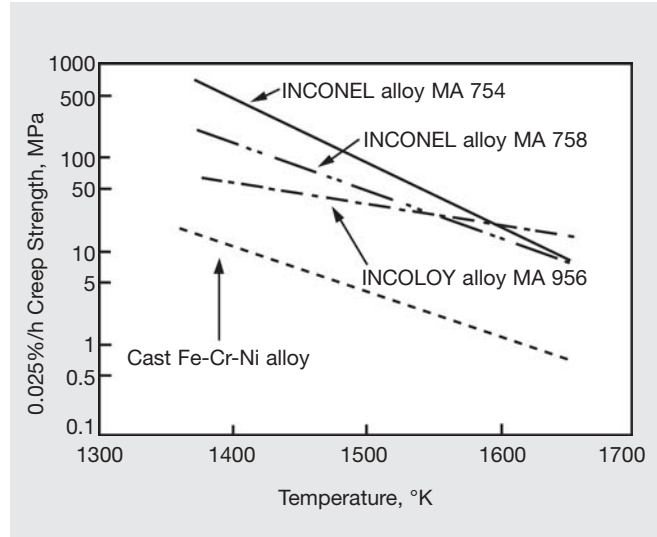


Figure 1. Creep strength at high temperatures.

Table 5 - Mechanical Properties of Bar*

Temperature		0.2% Yield Strength		Tensile Strength		Elongation
°C	°F	MPa	ksi	MPa	ksi	%
20	68	560	81.2	949	137.6	27
200	392	495	71.8	853	123.7	22
600	1112	421	61.0	741	107.4	23
700	1292	371	53.8	546	79.2	29
750	1382	274	39.7	429	62.2	41
800	1472	214	31.0	339	49.2	47
1000	1832	151	21.9	173	25.1	29

*Extruded round, annealed.

Table 6 - Mechanical Properties of Plate*

Temperature		Direction	0.2% Yield Strength		Tensile Strength		Elongation
°F	°C		ksi	MPa	ksi	MPa	%
68	20	Longitudinal	98.6	680	149.4	1030	14
68	20	Transverse	100.0	690	139.2	960	22
1800	982	Longitudinal	31.9	220	34.8	240	4
1800	982	Transverse	31.9	220	36.3	250	6
2000	1093	Longitudinal	24.7	170	26.1	180	4
2000	1093	Transverse	23.2	160	27.6	190	5

*9.5 mm (0.375 in) thick, annealed.

Corrosion Resistance

Resistance to Oxidation

Because of its high chromium content and the presence of yttrium particles in the matrix, INCONEL alloy MA 758 has outstanding oxidation resistance. Figure 2 shows how the alloy can perform at 1200°C (2200°F) and above for long periods without experiencing severe attack.

Resistance to Molten Glass

Environmental degradation at high temperatures involves the destruction of an alloy's protective scale, followed by penetration by harmful elements; sulfur, oxygen, nitrogen, etc. The exposure of an alloy to molten glass accentuates these problems because of the continuous fluxing of the alloy's protective scale.

INCONEL alloy MA 758 has shown excellent resistance to this type of attack. In a 5-day test at 1200°C (2190°F), the alloy was immersed in a "C" glass (65% SiO₂, 8.5% Na₂O, 14% CaO, 4% Al₂O₃, 5% B₂O₃, 3% MgO). It showed only 0.03 mm (0.001 inches) of attack after 5 days in this extremely aggressive environment.

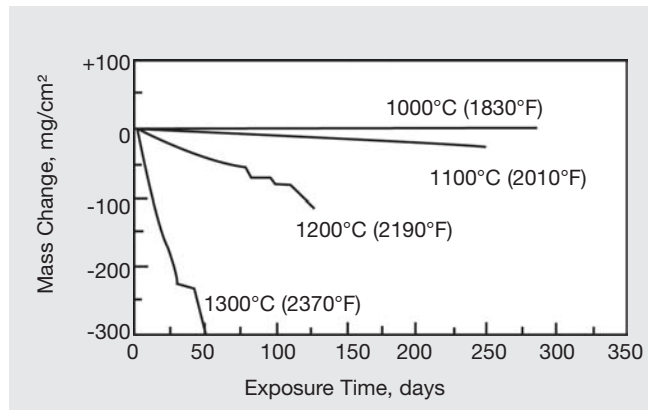


Figure 2. Effect of temperature on mass change of INCONEL alloy MA 758 in air.

Fabrication

Machining

INCONEL alloy MA 758 is readily machined in the fully recrystallized condition (HV 300-350) and has similar machining characteristics to solution-annealed INCONEL alloy 718.

Suggested conditions for single point turning are:

Depth of Cut		Carbide Tools						Tool Material
		Brazed		Throwaway		Feed		
		Speed		Speed				
in	mm	ft/min	m/min	ft/min	m/min	in/rev	mm/rev	
0.250	6.5	30-40	9-12	40-60	12-18	0.010	0.25	C-2
0.050	1.3	40-50	12-15	50-100	15-30	0.008	0.20	C-2

INCONEL alloy MA 758 can be readily machined using ordinary sulfurized mineral oil. Because of their greater cooling effect, water-based coolants are preferred for use in high speed operations such as turning, milling and grinding. These coolants may be soluble oil or proprietary chemical mixtures.

A soluble oil at a 15:1 dilution or a straight cutting oil of the extreme-pressure (EP), heavy-duty type is suggested. Except for grinding, which depends almost entirely on cooling and flushing, some chemical activity is desired, even in coolants, and is generally provided by chlorine, amines, or other chemicals.

For slower operations like drilling, boring, tapping and broaching, heavy lubricants and very rich mixtures of chemical coolants are desirable. The use of sulfurized oil may cause discoloration of the workpiece and is not recommended for use with cemented carbide tools since the heat generated at the point of the tool may cause the sulfur to attack the binding agent in the carbide.

It is important to remove all lubricants from machined pieces that are to be subjected to high temperatures either in fabrication or in service.

Fabrication, continued

Joining

Fusion Welding

INCONEL alloy MA 758 is weldable, usually for position welding and other applications that do not call for major stresses in service at the welded joints. In view of the extremely high strength of the alloy, the joints themselves will be of lower strength relative to the base metal. Tensile test results at 2000°F (1095°C) are shown in Table 7. The recommended welding consumable is INCONEL filler metal 52. INCONEL alloy MA 758 may also be joined by brazing.

Mechanical Fastening

Bolting, riveting, and other mechanical fastening methods are commonly used for joining INCONEL alloy MA 758 to itself and to other alloys.

Solid State Joining

In general, the mechanically alloyed materials are suitable for joining methods that involve solid state diffusion, such as bonding and friction welding.

Table 7 - Weld Transverse Tensile Tests at 2000°F (1095°C).
Gas-Metal-Arc Welded with INCONEL filler metal 52.

Post-Weld Heat Treatment	Ultimate Stress		Yield Stress ^a		Elongation
	ksi	MPa	ksi	MPa	%
As-welded	8.6	59.3	7.8	53.8	5.5
2400°F (1315°C)/1h/AC	10.2	70.3	10.1	69.6	7
Base metal longitudinal ^b	23.2	160	22.3	154	8.5
Base metal transverse ^b	23.6	163	23.4	161	6.1

^a Approximate yield strength

^b Average of 4 tests.

Available Product Forms

INCONEL alloy MA 758 is available in a range of commercial forms, including tube, plate, round bar and flat bar. Other forms can be made available for development projects of commercial significance.

The Special Metals Corporation
trademarks include: _____

BRIGHTRAY®
CORRONEL®
DEPOLARIZED®
DURANICKEL®
FERRY®
INCOBAR®
INCOCLAD®
INCO-CORED®
INCOFLUX®
INCOLOY®
INCONEL®
INCOTEST®
INCOTHERM®
INCO-WELD®
KOTHERM®
MONEL®

NILO®
NILOMAG®
NIMONIC®
NIOTHERM®
NI-ROD®
NI-SPAN-C®
RESISTOHM®
UDIMAR®
UDIMET®
601GC®
625LCF®
718SPF™
725NDUR®
800HT®
956HT™





U.S.A. Special Metals Corporation

Billet, rod & bar, flat & tubular products

3200 Riverside Drive
Huntington, WV 25705-1771
Phone +1 (304) 526-5100
+1 (800) 334-4626
Fax +1 (304) 526-5643

Billet & bar products

4317 Middle Settlement Road
New Hartford, NY 13413-5392
Phone +1 (315) 798-2900
+1 (800) 334-8351
Fax +1 (315) 798-2016

Atomized powder products

100 Industry Lane
Princeton, KY 42445
Phone +1 (270) 365-9551
Fax +1 (270) 365-5910

Shape Memory Alloys

4317 Middle Settlement Road
New Hartford, NY 13413-5392
Phone +1 (315) 798-2939
Fax +1 (315) 798-6860

United Kingdom

Special Metals Wiggin Ltd.

Holmer Road
Hereford HR4 9SL
Phone +44 (0) 1432 382200
Fax +44 (0) 1432 264030

Special Metals Wire Products

Holmer Road
Hereford HR4 9SL
Phone +44 (0) 1432 382556
Fax +44 (0) 1432 352984

China

Special Metals Pacific Pte. Ltd.

Room 1802, Plaza 66
1266 West Nanjing Road
Shanghai 200040
Phone +86 21 3229 0011
Fax +86 21 6288 1811

Special Metals Pacific Pte. Ltd.

Room 910, Ke Lun Mansion
12A Guanghua Road
Chaoyang District
Beijing 100020
Phone +86 10 6581 8396
Fax +86 10 6581 8381

France

Special Metals Services SA

17 Rue des Frères Lumière
69680 Chassieu (Lyon)
Phone +33 (0) 4 72 47 46 46
Fax +33 (0) 4 72 47 46 59

Germany

Special Metals Deutschland Ltd.

Postfach 20 04 09
40102 Düsseldorf
Phone +49 (0) 211 38 63 40
Fax +49 (0) 211 37 98 64

Hong Kong

Special Metals Pacific Pte. Ltd.

Unit A, 17th Floor, On Hing Bldg
1 On Hing Terrace
Central, Hong Kong
Phone +852 2439 9336
Fax +852 2530 4511

India

Special Metals Services Ltd.

No. 60, First Main Road, First
Block
Vasantha Vallabha Nagar
Subramanyapura Post
Bangalore 560 061
Phone +91 (0) 80 2666 9159
Fax +91 (0) 80 2666 8918

Italy

Special Metals Services SpA

Via Assunta 59
20054 Nova Milanese (MI)
Phone +390 362 4941
Fax +390 362 494224

The Netherlands

Special Metals Service BV

Postbus 8681
3009 AR Rotterdam
Phone +31 (0) 10 451 44 55
Fax +31 (0) 10 450 05 39

Singapore

Special Metals Pacific Pte. Ltd.

24 Raffles Place
#27-04 Clifford Centre
Singapore 048621
Phone +65 6532 3823
Fax +65 6532 3621

Affiliated Companies

Special Metals Welding Products

1401 Burris Road
Newton, NC 28658, U.S.A.
Phone +1 (828) 465-0352
+1 (800) 624-3411
Fax +1 (828) 464-8993

Canada House

Bidavon Industrial Estate
Waterloo Road
Bidford-On-Avon
Warwickshire B50 4JN, U.K.
Phone +44 (0) 1789 491780
Fax +44 (0) 1789 491781

Controlled Products Group

590 Seaman Street, Stoney Creek
Ontario L8E 4H1, Canada
Phone +1 (905) 643-6555
Fax +1 (905) 643-6614

A-1 Wire Tech, Inc.

A Special Metals Company
4550 Kishwaukee Street
Rockford, IL 61109, U.S.A.
Phone +1 (815) 226-0477
+1 (800) 426-6380
Fax +1 (815) 226-0537

Rescal SA

A Special Metals Company
200 Rue de la Couronne des Prés
78681 Epône Cédex, France
Phone +33 (0) 1 30 90 04 00
Fax +33 (0) 1 30 90 02 11

DAIDO-SPECIAL METALS Ltd.

A Joint Venture Company
Daido Shinagawa Building
6-35, Kohnan 1-chome
Minato-ku, Tokyo 108-0057, Japan
Phone +81 (0) 3 5495 7237
Fax +81 (0) 3 5495 1853